

Utilizing Green Glass Cullet, Local Ball Clay and White Clay For Producing Light Greenish Brown Color Wall Tile

Ubolrat Wangrakdiskul¹, Witsanu Loetchantharangkun²

¹ Production Engineering Department, Faculty of Engineering, King Mongkut's University of Technology North Bangkok, Thailand

² Production Engineering Department, Faculty of Engineering, King Mongkut's University of Technology North Bangkok, Thailand

ARTICLE INFO

Keywords:

*Local clay utilization,
Eco-friendly wall tile,
Green glass cullet*

ABSTRACT

This paper aimed to develop eco-friendly wall tiles from green color waste glass and local clay in Thailand. Owing to containing high fluxing agent, green glass cullet had been selected to develop wall tiles. It can reduce the sintering temperature of ceramic bodies. In addition, the green color of waste glass can promote the new texture of ceramic wall tiles. All materials used in this study consisted of green glass cullet (GGC), local ball clay (LBC), and local white clay (LWC). They were dried, milled, and sieved through a 50 mesh (297 micrometers) screen. Mixture formulations of materials had been conducted by using a tri-axial diagram. The rectangular specimens with dimension 50x100x7 mm were prepared by uniaxial pressing. They were all fired at 950oC with soaking for 1 h. Bending strength and water absorption of specimens were tested and compared with a Thai Industrial Standard (TIS 2508-2555). The results revealed that the formula contained 60% GGC, 30% LBC, and 10% LWC can achieve TIS 2508-2555. In addition, Scanning Electron Microscopy and X-Ray Diffraction technique were employed to characterize the microstructure of specimens. This can be summarized that utilizing waste glass and combining with local clay can develop eco-friendly fired clay wall tiles with light greenish brown texture.

1. Introduction

According to the policy of Thai government, it had been conducted for supporting the development of SMEs to achieve sustained and healthy economic growth [1]. This research was also performed for complying with this policy. Therefore, development of new products for saving energy and creating new texture product was proposed to the community ceramic

□ Corresponding Author E-Mail Address: ubolrat_w@hotmail.com

plant in Angthong province of Thailand. Consecutively, environmental problem of waste disposal is also the important concern. From the yearly report by the pollution control department in 2016 [2], 42% of waste glass in Thailand is not utilized, amounting to 1,014,653 tons.

There are many works studied about utilizing waste glass for manufacture of white ware ceramic bodies [3]. Youssef et al, had suggested the utilizing soda lime glass in wall and floor tiles which were fired at 1100°C [4]. In 2005, substitution waste glass in feldspar for making porcelain was proposed. It can reduce sintering temperature and make cheaper cost of material [5]. Braganca et al, had utilized sand from foundry industry, clay, and waste glass for producing white ware ceramics fired at 1100°, 1300°C. It can meet properties of Brazilian standards [6].

Roofing tiles with red color were produced at 750° C by mixing reddish yellow kaolinite clay and waste glass varying ratio from 0 to 15% [7]. Waste glass (WG) had been studied by substituting in feldspar (F) for producing porcelain stoneware tiles. The proportional of 5 WG and 25 F used fired range between 1000° - 1250° C were suggested [8].

In addition to studying white ware ceramic bodies, valorizing waste glass for fire clay bricks was also proposed by many researchers. Effect of waste glass on properties and durability of fired clay bricks had been investigated. The study suggested the proportion of fine and coarse particle size of waste glass and firing temperature at 1035° C [9]. Incorporation of waste glass in fired clay bricks can enhance their physical and mechanical properties [10, 11, 12, and 13].

Furthermore, local clays had been recognized for developing ceramic bodies as well. Thailand is one of countries in Asia having many resources i.e. kaolin clay, ball clay, and white clay, which can be utilized for producing ceramic products. White clay and ball clay, which are available in Prachinburi province [14], had been employed to combine with waste glass.

As reviewed researches mentioned above, substitution waste glass as fluxing agent for manufacturing low sintering fired clay wall tile was the objectives of this study. The expected results of this study was to create the light greenish brown color eco-friendly wall tile.

2. Materials and Methods

2.1 Materials

Three main materials used in this study consisted of GGC, LBC, and LWC. Their compositions were analyzed by X-ray fluorescence (XRF) method as shown in Tab 1. GGC played a role as reducing sintering temperature and promoting green color of ceramic tiles. Due to having plasticity, LBC and LWC were utilized for facilitating specimens' preparation. In addition, containing Fe₂O₃ in local clay can promote brown color in fired ceramic bodies. Tri-axial diagram was employed for formulation mixtures of the experiment. The six groups consisting of 33 formulas are conducted as shown in Tab 2. They are classified by varying % GGC quantities for each group.

Table 1: Chemical composition of materials used in this study by XRF technique

Compound	SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	K ₂ O	CaO	MgO	TiO ₂	MnO	P ₂ O ₅	Na ₂ O	SO ₃	BaO	Rb ₂ O	ZnO	ZrO ₂	Cr ₂ O ₃
Concentration (%)	GGC	69.9	1.91	0.43	0.36	10.8	1.24	0.08		14.6	0.07	0.09		0.03	0.03	0.3
	LBC	66.7	24.7	3.89	1.85	0.09	0.94	0.86	0.02	0.09	0.2	0.55	0.07	0.01	0.01	0.03
	LWC	58.4	37.9	2.11	0.19	0.04	0.13	1.06		0.06		0.09				0.06

Remark: GGC= Green Glass Cullet, LBC = Local Ball Clay, LWC = Local White Clay

Table 2: Formulation mixtures of the experiment

Group No.	A								B							C					D					E				F				
	A1	A2	A3	A4	A5	A6	A7	A8	B9	B10	B11	B12	B13	B14	B15	C16	C17	C18	C19	C20	C21	D22	D23	D24	D25	D26	E27	E28	E29	E30	F31	F32	F33	
Composition	GGC	10	10	10	10	10	10	10	20	20	20	20	20	20	20	30	30	30	30	30	30	40	40	40	40	40	50	50	50	50	60	60	60	
	LBC	10	20	30	40	50	60	70	80	10	20	30	40	50	60	70	10	20	30	40	50	60	10	20	30	40	50	10	20	30	40	10	20	30
	LWC	80	70	60	50	40	30	20	10	70	60	50	40	30	20	10	60	50	40	30	20	10	50	40	30	20	10	40	30	20	10	30	20	10

2.2 Methods

All mixture formulas were dried by electric oven and milled by pot mill in a lab scale to produce fine particles. They were sieved under 50 mesh (297 micrometer). Mixture of formulas were pressed by uniaxial pressing at 100 bar to form rectangular specimens of dimension 50x100x7 mm. Sintering temperature of specimens was set up at 950°C with 100°C/h and soaked for 1 h at maximum temperature. Then, fired specimens were tested the physical and mechanical properties which will be described as follows.

Bending strength of specimens was evaluated by three point bending using the equation of $3PL/bd^2$, where P is the load (force) at the fracture point (N), L is the length of the support span = 80 mm, b is width, and d is thickness of sample. Water absorption was determined by immersing the samples into water and boiling water with samples for 2 h and leaving them under water for 24 h. Then calculating a difference of dry and wet weight of specimens dividing by their dry weight. Bending strength and water absorption of test samples were carried out and compared with Thai Industrial Standard 2508-2555 (TIS 2508-2555). Linear shrinkage of fired specimen was determined by measuring the length before and after firing and dividing by its length before firing. Weight loss of fired specimens was evaluated. Weight loss of fired clay body was determined by measurement difference of its dry weight and fire weight body divided by its dry weight. Furthermore, bulk density of specimens was carried out by Archimedes technique.

In addition to testing physical and mechanical properties, microstructure of specimens was also investigated. X-ray Diffraction (XRD) pattern was carried out for analyzing the crystal phase of fired specimens. The phases occurred in the fired clay bodies were determined with X-ray diffraction (XRD), conducted on a Bruker D8 Advance diffractometer. The scanning electron microscopic (SEM) pattern was performed by Hitachi series SU3500 to analyze the crystal structure and porosity of specimen. The prepared samples were coated with the gold layer before testing. Results of test samples will be described in the following section.

3. Results and discussion

3.1 Mechanical and physical properties

As analyzing the composition of each material used (Tab 1), fluxing agent contents which lower the sintering temperature of ceramic bodies [12] are calculated. Comparison of fluxing agent in each formula with bending strength, linear shrinkage, weight loss is conducted (Tab 3). It shows that increasing fluxing agent content (Na₂O, K₂O, and CaO) has increased bending strength, linear shrinkage and weight loss. This can be summarized that effect of fluxing agent can enhance bending strength. Because they act as sintering aid for lower the sintering point of specimens. The highest strength value is 18.51 MPa of formula no. F33 having the highest fluxing agent. Linear shrinkage is also increased according to increasing of fluxing agent. Owing to having high carbonaceous matter [15], LBC (Local Ball Clay) has an effect on weight loss of fired specimens. Therefore, the highest content of LBC (formula no. A8) leads to high of weight loss.

Higher content of GGC makes lower density of specimens in group F (See Tab 4). However, bulk density of all formulas is slightly different, varying from 2.22 to 2.53. The value of water absorption of formula no. F33 having 60% wt. of GGC is the lowest value. In addition to enhance bending strength, fluxing agent in GGC leads to reduced porosity. Moreover, influence of LWC which having Al₂O₃ content higher than that of the others makes the high water absorption of specimens (formula no. A1).

Table 3: Composition, fluxing agent, bending strength, linear shrinkage, weight loss of 33 formulas

Group	No.	Composition			Physical and Mechanical Properties			
		GCG	LEC	LWC	%Fluxing	Bending S (MPa)	% Shrinkage	%Loss
A	A1	10	10	80	2.98	1.37	0.99	7.41
	A2	10	20	70	3.17	1.38	1.02	7.74
	A3	10	30	60	3.36	2.04	1.06	8.84
	A4	10	40	50	3.55	2.61	1.14	8.87
	A5	10	50	40	3.74	3.34	1.16	9.41
	A6	10	60	30	3.93	4.81	1.26	10.74
	A7	10	70	20	4.13	6.55	1.34	11.66
	A8	10	80	10	4.32	8.56	1.58	14.64
B	B9	20	10	70	5.54	2.20	1.19	6.46
	B10	20	20	60	5.73	3.31	1.22	6.60
	B11	20	30	50	5.92	3.58	1.27	6.84
	B12	20	40	40	6.11	4.06	1.29	6.94
	B13	20	50	30	6.30	6.71	1.54	7.12
	B14	20	60	20	6.49	7.16	1.61	7.30
	B15	20	70	10	6.68	8.43	1.68	8.87
C	C16	30	10	60	8.10	4.54	1.54	5.55
	C17	30	20	50	8.29	4.93	1.69	5.60
	C18	30	30	40	8.48	6.31	1.72	5.77
	C19	30	40	30	8.67	6.57	1.74	5.89
	C20	30	50	20	8.86	7.67	1.79	6.11
	C21	30	60	10	9.05	9.86	2.10	8.55
D	D22	40	10	50	10.65	6.36	1.79	5.32
	D23	40	20	40	10.84	7.95	2.15	5.51
	D24	40	30	30	11.04	8.43	2.17	5.77
	D25	40	40	20	11.23	8.68	2.36	6.26
	D26	40	50	10	11.42	10.13	2.39	7.86
	E	E27	50	10	40	13.21	7.63	2.30
E28		50	20	30	13.40	8.22	2.33	4.41
E29		50	30	20	13.59	10.63	2.35	4.78
E30		50	40	10	13.78	11.40	2.37	4.97
F	F31	60	10	30	15.77	16.57	2.59	4.17
	F32	60	20	20	15.96	16.97	2.60	4.41
	F33	60	30	10	16.15	18.51	2.61	4.81

Remark: Specimens contain >60% GGC unable to be performed

Table 4: Composition, bulk density, and water absorption of 33 formulas

Group	No.	Composition			Physical Properties	
		GCG	LBC	LWC	density (g/cc)	%absorption
A	A1	10	10	80	2.47	21.56
	A2	10	20	70	2.48	21.25
	A3	10	30	60	2.49	20.62
	A4	10	40	50	2.51	20.02
	A5	10	50	40	2.51	19.07
	A6	10	60	30	2.51	19.04
	A7	10	70	20	2.52	18.60
	A8	10	80	10	2.53	18.15
B	B9	20	10	70	2.44	19.07
	B10	20	20	60	2.46	17.99
	B11	20	30	50	2.46	17.97
	B12	20	40	40	2.46	17.91
	B13	20	50	30	2.46	17.40
	B14	20	60	20	2.46	16.61
	B15	20	70	10	2.46	16.36
C	C16	30	10	60	2.41	16.23
	C17	30	20	50	2.41	15.64
	C18	30	30	40	2.42	15.52
	C19	30	40	30	2.42	15.44
	C20	30	50	20	2.42	15.43
	C21	30	60	10	2.42	14.37
D	D22	40	10	50	2.39	14.80
	D23	40	20	40	2.39	13.80
	D24	40	30	30	2.4	13.73
	D25	40	40	20	2.4	13.52
	D26	40	50	10	2.41	13.36
	E	E27	50	10	40	2.32
E28		50	20	30	2.32	13.53
E29		50	30	20	2.32	12.82
E30		50	40	10	2.34	13.17
F	F31	60	10	30	2.22	11.44
	F32	60	20	20	2.22	11.25
	F33	60	30	10	2.23	11.13

3.2 Analyzing microstructure

Formula no. A1, C16, and F33 were selected based on its low, medium, and high bending strength, respectively. XRD pattern of them can be summarized in Tab 5. Crystallographic phase occurs in a test sample consist of Quartz, low Cristobalite and Wollastonite 2M. The composition of Wollastonite phase is CaSiO₃ which can improve bending or flexural strength [16]. Due to occurring Wollastonite phase, it can be summarized that formula C16 and F33 attain high bending strength. On the other hand, non-occurrence of Wollastonite 2M makes formula A1 has the highest water absorption.


Table 5: Phase content of selected formulas of XRD pattern

Formula no.	% Phase content			Bending Strength (MPa)
	Quartz	Low Cristobalite	Wollastonite 2M	
A1	84.75	15.25		1.37
C16	55.1	29.98	14.92	9.86
F33	50.37	31.67	17.96	18.51


Moreover, SEM patterns of selected formulas have been carried out as shown in Fig. 1. Fig 1(a) of formula expresses the microstructure having high porous. Meanwhile, microstructure of Fig 1(b) and 1(c) contain the glassy phase, especially Fig 1(c) also develops

Mullite ($3\text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2$) phase (needle like shape in white circles). This can be proved that formula no.F33 has the highest bending strength.

Fig. 1 SEM micrograph of specimens containing a) formula no.A1 with 10% wt GGC (5000X); b) formula no. C16 with 30 wt% GGC (5000X); c) formula no.F33 with 60 wt% GGC (5000X)

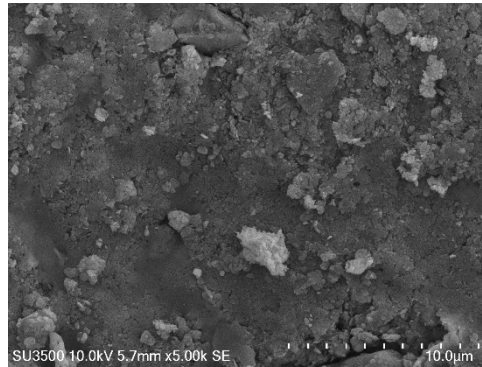

(a)

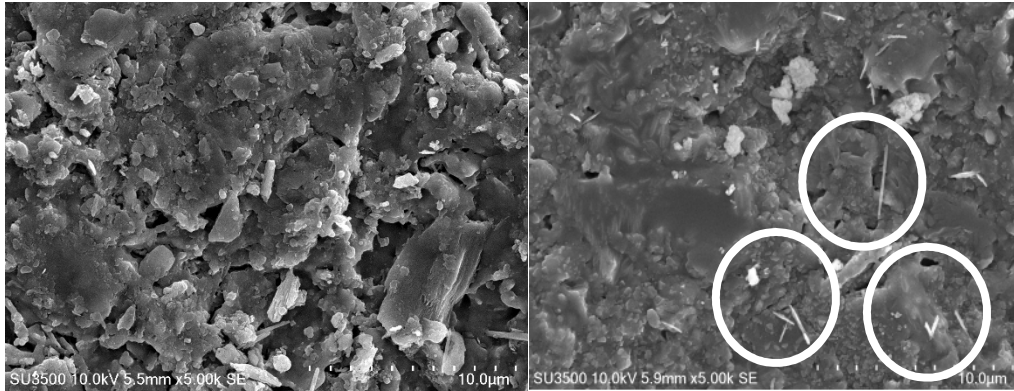

(b)

(c)

4. Conclusions

4.1 Comparison physical properties with TIS 2508-2555

Bending strength and water absorption were carried out and compared with TIS 2508-2555. Formulas that can achieve this standard are shown in Tab 6. They are all formulas of Group F.

Table 6: Bending strength and water absorption of formulas achieving TIS 2508-2555

TIS 2508-2555 (B III)		Bending St (MPa)	%Water absorption
		≥ 15	$>10\%$ Each sample must not exceed 20%
Formula No.	F31	16.57	11.44
	F32	16.97	11.25
	F33	18.51	11.13

4.2 Comparison the best formula with fired clay products of community industry

Formula no. F33 has the best properties for this research. Its properties have been compared with the community industry's specimens which fired at the same temperature; 950°C. They are shown in Tab 7, which can be concluded that effect of waste glass in the test sample can enhance its bending strength.

Table 7: Comparison properties of formula no. F33 and fired clay bodies of community industry

Formula	Properties				
	Bending Strength (MPa)	% Absorption	% Shrinkage	% Weight Loss	Density (g/cc)
No. F33	18.51	11.13	2.61	4.81	2.23
Fired clay of community industry	2.48	20.80	0.44	7.40	2.57

4.3 Implementation of this research work

This research can develop wall tiles that achieve the criteria of Thai Industrial Standard (TIS 2508-2555). It can be addressed that eco-friendly wall tiles utilizing green glass cullet (GGC) is a challenge work. This can produce new products in the community ceramic industry focusing on Angthong province. Light greenish brown wall tiles were developed for responding to the needs of customers who prefer the products variety.

4.4 Suggestions and future work

Although this work is able to meet the research objectives. Using waste glass more than 50% weight makes the difficult work for preparing the specimens due to low plasticity of green glass cullet (GGC). Therefore, adding binder for facilitating forming work pieces should be performed. In addition, utilizing other waste materials should be investigated i.e. sediment soil from water supply treatment process, solid waste of palm oil fuel ash.

Acknowledgements

The authors would like to thank the anonymous referees for their useful suggestions. This research was funded by Thailand OHEC Talent Mobility Program 2018, Office of Higher Education Commission, Ministry of Education.

References

- [1] Turner, M. Sermcheep, S. Anantasirijkiat, S. and Srisangnam, P. (2016). "Small and medium-sized enterprises in Thailand: government policy and economic development Asia Pacific," *J Public Administration* Vol. 38, pp. 251-269.
- [2] Pollution Control Department, Ministry of Natural Resources and Environment, Thailand State of Pollution Report 2016. (2017), Available: <http://www.pcd.go.th>. (Accessed 3 November 2017).

- [3] Silva, R.V. Brito, de J. Lye, C.Q. and Dhir, R.K. (2017). “The role of glass waste in the production of ceramic-based products and other applications: A review,” *Journal of Cleaner Production*. 167, pp. 346–364.
- [4] Youssef, N.F. Abadir, M.F. and Shater, M.A.O. (1998). “Utilization of Soda Glass (Cullet) in the Manufacture of Wall and Floor Tiles,” *Journal of European Ceramic Society*. Vol18(12), pp. 1721-1727.
- [5] Bragança, S.R. and Bergmann, C.P. (2005). “Waste Glass in Porcelain,” *Material Research*. Vol 8 (1), pp. 39-44.
- [6] Braganca,S.R. Licenzi, Guerino, J. K. and Bergmann, C.P.(2006). “Recycling of iron foundry sand and glass waste as raw material for production of whiteware.” *Waste Management Research*. Vol 24, pp. 60–6.
- [7] Tiffo, E. Elimbi, Manga, A. J. D. and Tchamba, A. B. (2015). “Red ceramics produced from mixtures of kaolinite clay and waste glass,” *Brazillian Journal of Science and Technology*. Vol 2(4), pp. 1–13.
- [8] Luz, A.P. and Riberio, S.(2007). “Use of glass waste as a raw material in porcelain stoneware tile mixtures,” *Ceramic International*. Vol 33, pp.761–765.
- [9] Chidiac, S.E. and Federico, L.M. (2007). “Effects of waste glass additions on the properties and durability of fired clay brick,” *Canadian Journal of Civil Engineering*. Vol 34(11), pp. 1458-1467.
- [10] Loryuenyong, V. Panyachai, T. Kaewsimork, K. and Siritai, C. (2009). “Effects of recycled glass substitution on the physical and mechanical properties of clay bricks,” *Waste Management*. Vol 29, pp. 2717-2721.
- [11] Demir, I. (2009) “Reuse of waste glass in building brick production,” *Waste Management Research*. Vol 27, pp. 572-577.
- [12] Phonphuak, N. Kanyakam, S. and Chindaprasirt, P. (2016). “Utilization of waste glass to enhance physical-emechanical properties,” *Journal of Cleaner Production*. Vol 112, pp. 3057–3062.
- [13] Wiemes, L. Urivald, P. and Mymrin, V. (2016) “Incorporation of industrial wastes as raw materials in brick's formulation,” *Journal of Cleaner Production*. Vol 142, pp.69-77.
- [14] Department of Primary Industries and Mines, Ministry of Industry, DPIM Economic Review, January (2018). <http://www.dpim.go.th/purchase/mainarticle?catid=137>. (Accessed 1 November 2018).
- [15] Information on <https://sanitaryware.org/article/ball-clay>
- [16] Information on <https://en.wikipedia.org/wiki/Wollastonite>